

#### **Article Information**

Submitted: November 24, 2023
Approved: December 13, 2023
Published: December 14, 2023

How to cite this article: Harichane A, Belalia F. Influence of Polycarboxylate Superplasticizer on the Calorimetric and Physicomechanical Properties of Mortar. IgMin Res. Dec 14, 2023; 1(2): 133-135. IgMin ID: igmin128; DOI: 10.61927/igmin128; Available at: www.igminresearch.com/articles/pdf/igmin128.pdf

Copyright license: © 2023 Harichane A, et al. This is an open access article distributed under the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

**Keywords:** Cement; Calorimeter; Hydration; Resistance; Polycarboxylate superplasticizer

#### **Research Article**

Influence of Polycarboxylate Superplasticizer on the Calorimetric and Physicomechanical Properties of Mortar

# Alya Harichane\* and Fatiha Belalia

Institute of Science, University Center of Tipaza, 42000, Algeria

\*Correspondence: Alya Harichane, Institute of Science, University Center of Tipaza, 42000, Algeria, Email: harichane.alya@cu-tipaza.dz



#### **Abstract**

The use of polycarboxylate ether superplasticizer PCE in the preparation of mortars and concretes influences the hydration kinetics and the amount of total heat released. This leads to a modification of certain properties of the mortar, namely workability, calorimetry and mechanical resistance. In this study two ether polycarboxylate superplasticizers with different chemical structures were used; they were incorporated at different dosages into a standardized cement-based mortar. The objective of this work is to study the effectiveness of these superplasticizers and to select the most compatible product with cement and the most suitable for use according to the climates of the country. The impact of superplasticizers on fresh cement was studied by measuring the Marsh cone flow time and calorimetric measurement. In the hardened state, the mechanical properties were provided by measuring the compressive strength. The results show that low dosages of ether polycarboxylate superplasticizer promote grain hydration and produce more heat. On the other hand, high dosages delay the contact of the cement grains with the mixing water and cause a reduction in the final heat released and a delay in setting. The ether polycarboxylate superplasticizer with high carboxylic density gives the best mechanical resistance compressive at 7 and 28 days.

### Introduction

Among the most important superplasticizers currently used in the preparation of concrete, we find polycarboxylates [1], preferred for their ability to improve the properties of concrete [2,3] and to give it better mechanical behavior due to the reduction in the necessary W/C ratio. The type of polycarboxylate used and its molecular structure influence the rheological behavior of the pastes [4-6]. These polymers influence the heat of hydration as well as the quantity of hydration products formed. Their dispersion effect is linked to adsorption which depends on the compatibility between superplasticizer and cement. The dispersion of grains promotes direct contact with the mixing water, which increases the quantity of hydrates formed and improves the mechanical properties of mortars or concretes.

The aim of our study is to compensate for the lack of information by analyzing the effect of two polycarboxylates of different chemical structures on the physico-mechanical and calorific properties of cement pastes.

# **Materials and methods**

### **Materials**

**Superplasticizer:** Two types of superplasticizers produced in Algeria were used: Medaflow 30 - designated as PCE1 and Polyflow SR 5400 - designated as PCE2. The two polymers are new-generation, non-chlorinated, and are based on modified polycarboxylic ether. The characteristics of the superplasticizers, according to their technical data sheet, are presented in Table 1.

Table 1: Properties of the PCEs.

Drananti	Type of superplasticizer				
Property	PCE <sub>1</sub>	PCE <sub>2</sub>			
Dry extract	30% ± 1%	30% ± 1%			
рН	3.35	4.46			
Density (g/cm³)	1.07 ± 1	1.07 ± 0.02 13 621			
Mn (Da)	4 771				
Mw (Da)	5 157	15 959			
PDI	1.081	1.172			
Carboxyl content (mmol/g)	1.95	1.87			
DDI: Dolydianaraity Inday: Mn: Number	s average melecular	weight of DCE: Mar			

PDI: Polydispersity Index; Mn: Number average molecular weight of PCE; Mw. Weight average molecular weight of PCE

DOI: 10.61927/igmin128 ISSN 2995-8067

Portland cement: The cement used in this work is a composite portland cement (CEM II/ A-L 42.5 N) containing 17% clay, 80% limestone, 2% sand and 1% iron ore, produced by the company Mitidja Cements; Algeria. The chemical, mineralogical, and physical characteristics are shown in Table 2.

#### **Experimental measurements**

Compressive strength: The compressive strength was measured according to the EN 196-1 protocol. A batch of three mortar specimens was prepared with cement, water, standard sand (c:w:s = 1: 0.5: 3), and super-plasticizers (P/C = 0; 0.2; 0.4; 0.6; 0.8; 1%). After casting for 1 day, samples were demoded and cured in water for 1, 7 and 28 days. The compressive strengths of the samples were determined.


**Hydration heat:** A semi-adiabatic calorimeter was chosen to measure the heat of hydration of mortar samples prepared with one part cement, three parts sand, and half part water. The mixtures are adjuvanted with different dosages and types of superplasticizers. The mixtures are made with different superplasticizer contents, 0.0.5, 1, 1.5, 2%.

#### **Results and discussions**

#### Compressive strength

Figure 1 shows that SP1 gives the best mechanical compressive strength at 7 and 28 days; he is the most efficient. SP1 is a polycarboxylic ether-type superplasticizer; it is the most efficient. This copolymer has a comb structure; its main chain carries a negatively charged carboxylic group which facilitates the adsorption of the molecule on the surface of the cement particles by electrostatic interaction; The side chains contain polyethylene glycol (PEG) structures that promote dispersion of cement particles due to the steric hindrance they produce [1,2,4]. SP1 is

Table 2: Chemical and Mineralogical composition of the cement.										
Chemical characteristics										
designation	PAF	SiO <sub>2</sub>	Al <sub>2</sub> O <sub>3</sub>	Fe <sub>2</sub> O <sub>3</sub>	CaC	О	MgO	SO <sub>3</sub>	K <sub>2</sub> O	Na <sub>2</sub> O
%	7.57	19.43	4.69	3.24	63.7	79	1.40	2.25	0.69	0.22
Mineralogical characteristics										
designation	С	3S	C2S			C3A			C4AF	
%	75	5.83	1.49			6.95			9.86	

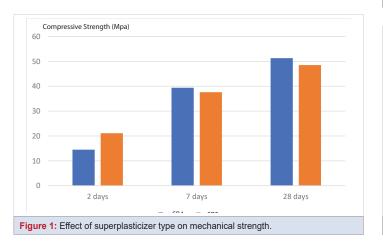

more efficient compared to SP2; due to its higher carboxylic charge density; the latter improves the dispersion of cement grains and promotes direct contact with the mixing water, which increases the quantity of hydrates formed and improves the mechanical properties of mortars or concretes.

# **Hydration heat**

Figures 2,3 illustrate the evolution of the total exothermic heat provided by different dosages of each superplasticizer. By adding superplasticizer to the mortar, the final heat decreases with increasing superplasticizer dosage; due to the dispersion of grains and the availability of water released by their deflocculation. The superplasticizers delay the contact of the cement grains with the mixing water and cause a reduction in the final heat. Polycarboxylate molecules prefer to attach to C3A and C4AF and their hydration products and delay the hydration of C3S and the formation of CSH and CH [7]; after the addition of 0.5% of a polycarboxylate, the formation of portlandite began after 18 hours of hydration, on the other hand for an ordinary cement without superplasticizer it began after 4 hours. Polycarboxylates delay initial hydration for a long time, since the thickness of the superplasticizer absorption layer interferes with ion diffusion, on the other hand when Ca+2 ions saturate the surface, the growth of CH eliminates the layer doubles and diffuses the silicates to the surface of the solution [7].

SP1 is the most efficient; it reduces the heat of hydration to 218 J/g after 3 days due to its chemical structure. The carboxylic


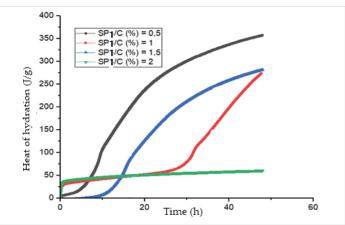


Figure 2: Influence of the SP1 dosage on the heat of hydration of a cement mortar.

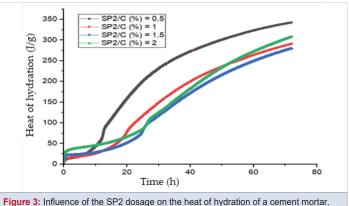

ISSN 2995-8067 DOI: 10.61927/igmin128

density and molecular weight of the superplasticizer have great effects on the dispersion performance. As the carboxylic density increases, the dispersion capacity of the SP improves [8-10]. PCE1 has the highest carboxylic density in the backbone and moderate molecular weight and has higher adsorption behavior on cement particles; therefore, the lowest heat of hydration. It is therefore compatible with cement.

## **Conclusion**

Superplasticizers are used to improve the mechanical and calorimetric properties of cementitious systems. These anionic polymers adsorb on the surface of the cement grains and cause dispersion of the particles. Fluidity is thus obtained by the deflocculation of the cement grains and the release of the water retained in the flocculates. A consecutive reduction in the heat of hydration as a function of the superplasticizer dosage is then mentioned.

#### References

- Harichane A, Benmounah A. Influence of Polycarboxylic Ether-based Superplasticizers (PCE) on the Rheological Properties of Cement Pastes. J Mater Eng Struct. 2021; 8: 325–339.
- Lei L, Hirata T, Plank J. 40 years of PCE superplasticizers-History, current state-of-the-art, and an outlook. Cem Concr Res. 2022; 157: 106826
- 3. Harichane A, Seghir NT, Niewiadomski P, Sadowski Ł. Effectiveness

- of the Use of Polymers in High-Performance Concrete containing Silica Fume. Polymers. 2023; 15(18): 3730. https://doi.org/10.3390/polym15183730
- Harichane A, Benmounah A, Plank J. Effect of Molecular Weight and Carboxylic Density of Polycarboxylates Ether Superplasticizer on Its Performance in Cement Pastes. J Mater Eng Struct. 2023; 10: 283-292.
- Sha S, Wang M, Shi C, Xiao Y. Influence of the structures of Polycarboxylate superplasticizer on its performance in ce-mentbased materials-a review. Constr Build Mater. 2020; 233: 117257
- Kai K, Heng Y, Yingbin W. Effect of chemical structure on dispersity of polycarboxylate superplasticizer in cement paste. Adv Cem Res. 2019; 32: 456–464.
- Chen S, Sun S, Chen X, Zhong K. Effects of core-shell polycarboxylate superplasticizer on the fluidity and hydration behavior of cement paste. Colloids and Surfaces A: Physicochemical and Engineering Aspects. 2020; 590: 124464. doi:10.1016/j.colsurfa.2020.124464.
- Kong F, Pan L, Wang C, Zhang D, Xu N. Effects of polycarboxylate superplasticizers with different molecular structure on the hydration behavior of cement paste. Construction and Building Materials. 2016; 105:545-553. doi:10.1016/j.conbuildmat.2015.12.178.
- 9. Papo A, Piani L. Effect of various superplasticizers on the rheological properties of Portland cement pastes. Cement and Concrete Research. 2004; 34(11): 2097-2101. doi:10.1016/j.cemconres.2004.03.017.
- Alonso MM, Palacios M, Puertas F. Compatibility between polycarboxylate-based admixtures and blended cement pastes. Cement and Concrete Composites. 2013; 35(1): 151-162. doi:10.1016/j. cemconcomp.2012.08.020.

How to cite this article: Harichane A, Belalia F. Influence of Polycarboxylate Superplasticizer on the Calorimetric and Physicomechanical Properties of Mortar. IgMin Res. Dec 14, 2023; 1(2): 133-135. IgMin ID: igmin128; DOI: 10.61927/igmin128; Available at: www.igminresearch.com/articles/pdf/igmin128.pdf

IgMin Research in SCIENCE December 14, 2023 - Volume 1 Issue 2

IgMin Research   STEM, a Multidisciplinary Open Access Journal, welcomes original contributions In addressing Article Processing Charges (APCs), IgMin Research: STEM recognizes their significance of the state of t					
from researchers in <b>S</b> cience, <b>T</b> echnology, <b>E</b> ngineering, and <b>M</b> edicine (STEM). Submission	in facilitating open access and global collaboration. The APC structure is designed for affordability and				
guidelines are available at www.igminresearch.com, emphasizing adherence to ethical	al transparency, reflecting the commitment to breaking financial barriers and making scientific research				
standards and comprehensive author guidelines. Manuscripts should be submitted online to accessible to all.					
submission@igminresearch.us.  For book and educational material reviews, send them to STEM, IgMin Research, at support@igminresearch.us. The Copyright Clearance Centre's Rights link program manages article permission requests via the journal's website (https://www.igminresearch.com). Inquiries about Rights link can be directed to info@igminresearch.us or by calling +1 (860) 967-3839.	1				
https://www.igminresearch.com/pages/publish-now/author-guidelines	https://www.igminresearch.com/pages/publish-now/apc				
WHY WITH US					
<b>IgMin Research</b>   STEM employs a rigorous peer-review process, ensuring the publication of high-quality research spanning STEM disciplines. The journal offers a global platform for researchers to share groundbreaking findings, promoting scientific advancement.					
JOURNAL INFORMATION					

APC

mailed to submission@igminresearch.us

INSTRUCTIONS FOR AUTHORS

Organized by: IgMin Publications Inc.

#### License: Open Access by IgMin Research is Journal Full Title: IgMin Research-STEM | A Multidisciplinary Open Access Journal Regularity: Monthly Journal NLM Abbreviation: IgMin Res Review Type: Double Blind licensed under a Creative Commons Attribution 4.0 Journal Website Link: https://www.igminresearch.com Publication Time: 14 Days International License. Based on a work at IgMin

Category: Multidisciplinary GoogleScholar: https://www.igminresearch.com/gs Publications Inc.

Subject Areas: Science, Technology, Engineering, and Medicine Plagiarism software: iThenticate Online Manuscript Submission:

**Topics Summation:** 173 https://www.igminresearch.com/submission or can be Language: English

Collecting capability: Worldwide